

INTERNATIONAL RESEARCH FELLOWS ASSOCIATION'S

RESEARCH JOURNEY

International E-Research Journal

Peer Reviewed, Referred & Indexed Journal

Issue -292 (C)



Executive Editors of the issue

Dr. Raj Kishor Tripathi

Dr. Lalit Gupta

Shri Ramdas Verma

Dr. Yogesh Shukla

Dr. Aditya Kumar

Dr. Ananad Singh

Chief Editor : Dr. Dhanraj Dhangar





'RESEARCH JOURNEY' International E- Research Journal

Issue – 292 (C) : Multidisciplinary Issue

Impact Factor : 6.625

Peer Reviewed Journal

E-ISSN :

2348-7143

April-2022

April-2022

E-ISSN – 2348-7143

INTERNATIONAL RESEARCH FELLOWS ASSOCIATION'S

RESEARCH JOURNEY

International E-Research Journal

Peer Reviewed, Referred & Indexed Journal

Issue – 292 (C)

Executive Editors of the issue

Dr. Raj Kishor Tripathi

Dr. Lalit Gupta

Shri Ramdas Verma

Dr. Yogesh Shukla

Dr. Aditya Kumar

Dr. Ananad Singh

Chief Editor : **Dr. Dhanraj Dhangar**



Our Editors have reviewed papers with experts' committee, and they have checked the papers on their level best to stop furtive literature. Except it, the respective authors of the papers are responsible for originality of the papers and intensive thoughts in the papers. Nobody can republish these papers without pre-permission of the publisher.

- Chief & Executive Editor

SWATIDHAN INTERNATIONAL PUBLICATIONS

For Details Visit To : www.researchjourney.net

*Cover Photo (Source) : Janta College, Etawah, Bakewar, Uttar Pradesh.

© All rights reserved with the authors & publisher

Price : Rs. 1000/-

Published by –

© Mrs. Swati Dhanraj Sonawane, Director, Swatidhan International Publication, Yeola, Nashik

Email : swatidhanrajs@gmail.com Website : www.researchjourney.net Mobile : 9665398258

INDEX

No.	Title of the Paper	Author's Name	Page No.
01	Cardiovascular Disease Classification from Imbalanced Healthcare Data Using Improved SMOTE Technique	R.Saranya, Dr. D. Kalaivani	05
02	Libraries : Supporting Education in India During Pandemic	Mrs. Shilpa Jadhav	11
03	Role of Library Science Professionals in Academic Libraries	Dr. Roopa Gokhale	15
04	Long Life Learning Opportunity through Digital Libraries as Facilitators of E-Learning	Mr. Devidas Phad	19
05	MOODLE : An Effective E-learning Platform in Higher Education	Ms. Kartika Mahajan, Dr. Vaishali Gudadhe	27
06	Prediction of Diabetes Using Machine Learning Algorithms in Healthcare	Mrs. S. Ramya, Dr. D. Kalaivani	34
07	An Experimental Study to Assess the Effectiveness of Awareness Campaign Regarding Blood Donation on Knowledge Attitude & Participation Among College Students at Selected College in Bhilai Dist-Durg,C.G.	Ms. Mamta Sinha	40
08	A Review of Image Mining - Face Detection and Recognition	Dr. V. Ganesh Babu	47
09	To Study the Effect of Reaction Conditions on the Thermal Polymerization of Vinyl Monomers Initiated By 1,1,2,2- Tetraphenyl Ethane Diol	Pranjit Kumar Bhuyan	50
10	Analysis of Food Consumption in Rural Areas Concerned with Government Plans of District Etawah (U.P.)	Dr. Padma Tripathi	59
11	Study of Light Effect on Spore Germination in Some Pteridophytic Taxa	Ritu Jain, B.L. Yadav	63
12	Awareness and Utilization of Open Educational Resources (OER) in Higher Education Students	Elango. M , Karpaga Kumaravel. R	67
13	Natural Dyeing on Cotton and Cotton Khadi With Varieties of Tea Leaves (Camellia Sinensis) Using Natural Mordants	Dr. (Mrs.) Vishaka Karnad , Ms. Shivani Jaju	75
14	The Role of Librarian in the Smart Learning Environment	Dr.T. Prabakaran, Dr. G. K. Ashok	89
15	Demographic Factors Influence on Faculty Members Work Life Balance	Yogambal. N, Dr. P. Karthikeyan	94
16	Decoding the Law: POCSO Act	Mrs. Dipali Patil	97
17	Uncommon Tribal Marriage Customs in India with Reference to Todas	Dr. S. Kamala Devi	103
18	Effects of Application of Fertilizers on Soil Ph, EC and Organic Carbon Content in Soil Under Intensive Cropping	Dr. Rajesh Kishor Tripathi	113
19	Evolution of User's Satisfaction with Library Resources & Services Maharashtra State College of Management ASM'S IBMR Pune : A Study	Ms. Rajshri Gadkari, Dr.Bhagyashri Keskar	117
20	Role of Constitution in the Legal System of India	Mrs. Ashwini Lele	122
21	An Investigation of Attitudes towards M.Ed. Students Research Work in Karur District	Dr. B. Murugesan	128

22	Bibliometric Analysis of Scientific Productivity : A Study of Arts, Commerce Colleges	Manoj Dongardive	133
23	Study of Facile Chemically Synthesized Polythiophene Thin Films	Deepak Shirgaonkar, S. D. Pawar	141
24	Emotional Intelligence of Higher Secondary Students in Karur District	Dr. P. Subasini	146
25	Change Literacy in Rajasthan : A Geospatial Analysis	Prasanta Mujrai, Dr. Dharmendra Singh	150
26	Significance of Total Quality Management Principles in Libraries : An Overview	Usha Sharma, Dr. Ashok Upadhyay	158
27	New Education Policy-2020 and Libraries	Keertee Parchure	163
28	Role of Teachers During Covid-19 : An Overview	Dr. Rafiya	168
29	Positive Energy and Effective Communication	Dr. Surekha Verma	174
30	A Study On – 'Investors Attitude towards Investing in Cryptocurrency' – With Reference to Mumbai Region	Prof. Utkarsh Kapadia	177
31	Rural Development through Information Literacy Programme	Mrs. Dawa Doma Sherpa	185
32	Social and Political Women Empowerment - Issues and Challenges	V. Sandhya	193
33	Utilization of Internet and Social Networking Sites in Digital Resource Sharing in Libraries	Dr. Roopa Gokhale	198
34	कोव्हीड-19 चे भारतीय अर्थव्यवस्थेतील परिणाम	प्रा. एस्. एन. जाधव	207



SWATIDHAN INTERNATIONAL PUBLICATIONS

For Details Visit To : www.researchjourney.net

Issue No. 292 (C)

*Cover Photo (Source) : Janta College, Etawah, Bakewar, Uttar Pradesh.

© All rights reserved with the authors & publisher

Price : Rs. 1000/-

Published by -

© Mrs. Swati Dhanraj Sonawane, Director, Swatidhan International Publication, Yeola, Nashik

Email : swatidhanrajs@gmail.com Website : www.researchjourney.net Mobile : 9665398258

Study of Facile Chemically Synthesized Polythiophene Thin Films

Deepak B. Shirgaonkar^{a*}, S. D. Pawar^b

^aDepartment of Physics, Anandibai Raorane Arts, Commerce and Science College, Vaibhavwadi, Sindhudurg, M.S., India.

^bDepartment of Physics, A. C. S. College, Palus, M.S., India.

Abstract:

Polythiophene thin film were synthesized by using chemical polymerization technique (CBD) at room temperature and deposited on glass substrate. The chemical bonding, surface morphological and optical properties were studied using FT-IR, FE-SEM, AFM, UV-Visible spectroscopy. The study of chemical bonding nature clearly indicating the characteristic IR absorption bands of polythiophene. The surface morphological study revealed that the nanofibrous polythiophene morphology. The water contact angle were measured, shows the surface behavior of film with water.

Keywords: Chemical Bath Deposition, Polymer, Polythiophene-thin film, Field Emission Scanning Electron Microscopy (FE-SEM), Optical properties.

1. Introduction

Now a day, due to the electrical, chemical or physical properties, lot of development has taken place in the of conducting polymers such as polythiophene (PTh), polyaniline (PANI), polypyrrole (PPy) and their derivatives. One of the conducting polymers, polythiophene and its derivatives have been studied for several applications in optoelectronics i.e. supercapacitor, field effect transistors, photovoltaic and photoconductive devices, sensor, light emitting diodes, etc.[1-5]. The electronics and optical properties of the films are characteristically depend on its local structure for the operation of the devices.

In this work we report the formation of nanofibers of polythiophene by using chemical synthesis (chemical bath deposition technique). The surface morphology, optical properties and water contact angle were reported.

2.1 Experimental

The nanofibrous polythiophene were synthesized using the chemicals, thiophene (AR grade 99% Aldrich chem. Ltd.), ferric chloride (AR grade, 98% Thomas Baker Pvt. Ltd.), Chloroform (AR grade, 99.4%, Thomas Baker Pvt. Ltd.), and methanol (AR grade, 99.5%, Spectrochem Pvt. Ltd.)

2.2 Synthesis of Polythiophene thin film

By using ferric chloride as a oxidant and thiophene as monomer, nanofibrous polythiophene thin film were synthesized by using chemical polymerization. Thiophene were dispersed in chloroform to make monomer solution, however, FeCl₃ was dissolved in chloroform to get oxidant solution. Thiophene prepared with different molar solution as 0.5, 1.0, 1.5, 2.0 M and oxidant with 1.5 M.

Both the solution were prepared in 50 ml anhydrous chloroform with constant stirring for 30 min. simultaneously. The oxidant solution added in monomer solution with constant volume after constant interval of time (15 min) and continuous stirring of solution. The vertically dipped glass substrate in the solution are provide the adherent coefficient to deposit thin film on the

glass. With addition of oxidant the reaction is initiated and the color of solution change from brown to dark brown and at same time the film deposited on the glass substrate.

3. Physico-chemical characterization

Thin films were characterized by FTIR spectroscopy for nature of chemical bonding. Study of surface morphology was carried out using FESEM. Atomic force microscopy was used to study the topography of the deposited thin film. Absorption spectra of the films were obtained using UV-Visible spectrophotometer. The water adsorption study was carried by using wettability of the film.

3.1 Fourier Transform Infrared Spectroscopy (FTIR) analysis

Fourier Transform Infrared Spectroscopy analysis shows the nature of chemical bonding of polythiophene thin film in the range of 500-4000 cm^{-1} . Fig. 1 shows the FTIR spectra of polythiophene thin films. The absorption spectra in the range 600 to 1500 cm^{-1} shows the fingerprint region of polythiophene. The absorption band at 676 cm^{-1} (1) attributed to C-S stretching in the thiophene ring whereas at 781 cm^{-1} (2) shows C-H out of plane vibration. The band at 1089 cm^{-1} (3) assigned the C-H in plane stretching vibration [1,6]. The peak at 1339 cm^{-1} (5) and 1456 cm^{-1} (6) are shows C-C stretching vibration and C=C symmetric vibrations [7-9]. The band at 1732 cm^{-1} (7) arises due to presence of small amount of C=O [10]. These peaks reveal that the polymerization of thiophene monomer.

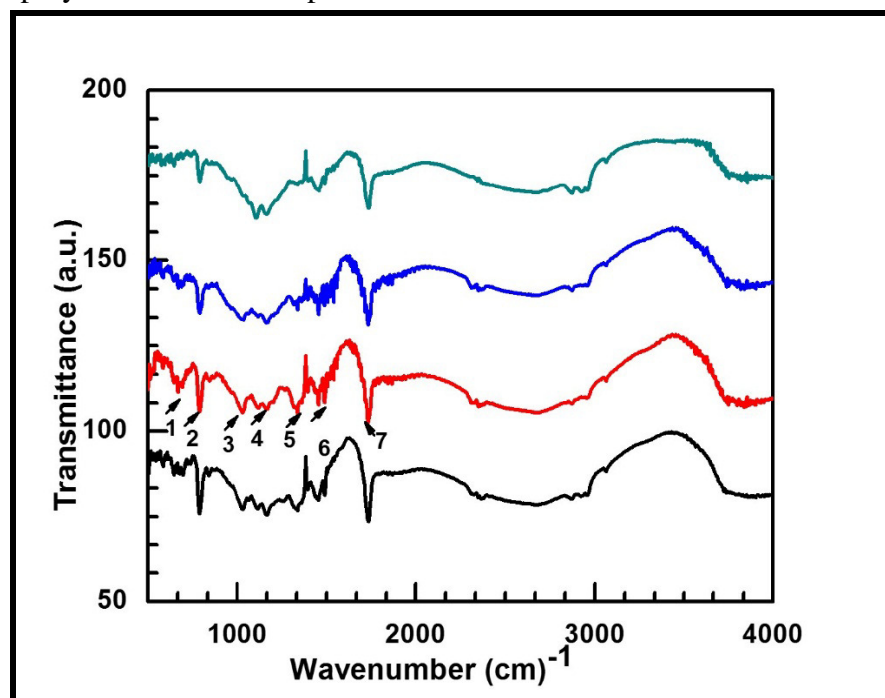


Fig. 1. FTIR spectra of polythiophene thin films deposited at (a) 0.5, (b) 1.0, (c) 1.5 and (d) 2.0 M thiophene concentration.

3.2 Field Emission Scanning Electron Microscopy (FESEM)

FESEM images shows the surface morphology of the polythiophene thin film. Fig 2 shows that the fibrous structure of the film of average diameter is in the range of some nanometer, which provides large surface area. The fibers are connected with each other. Hence mesh like structure is formed.

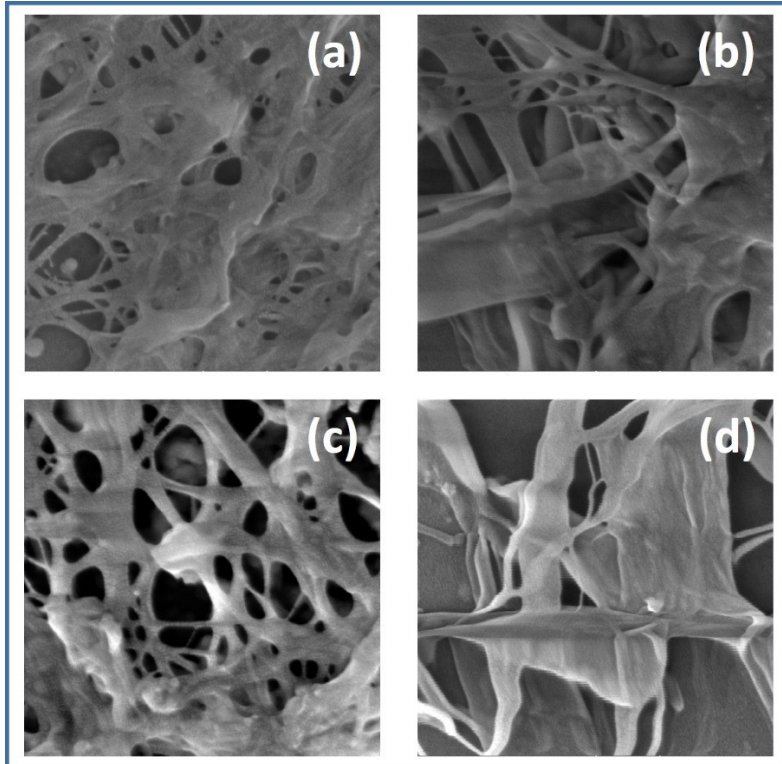


Fig. 2 FESEM micrographs of polythiophene thin films deposited at (a) 0.5, (b) 1.0, (c) 1.5 and (d) 2.0 M thiophene concentration.

3.3 Atomic Force Microscopy (AFM)

Atomic force microscopy images for all the films were recorded in non-contact mode Fig. 3. The Fig. 3 reveal that the effect of concentration variation on the film growth. The budlike structure is formed. The number of spikes increases with increase in monomer concentrations. The roughness is also vary with the concentrations shows in Table 1.

Table 1. Roughness of polythiophene thin films (a) 0.5, (b) 1.0, (c) 1.5 and (d) 2.0 M.

Sample	a	b	c	d
Roughness (nm)	2.78	3.27	18.1	3.66

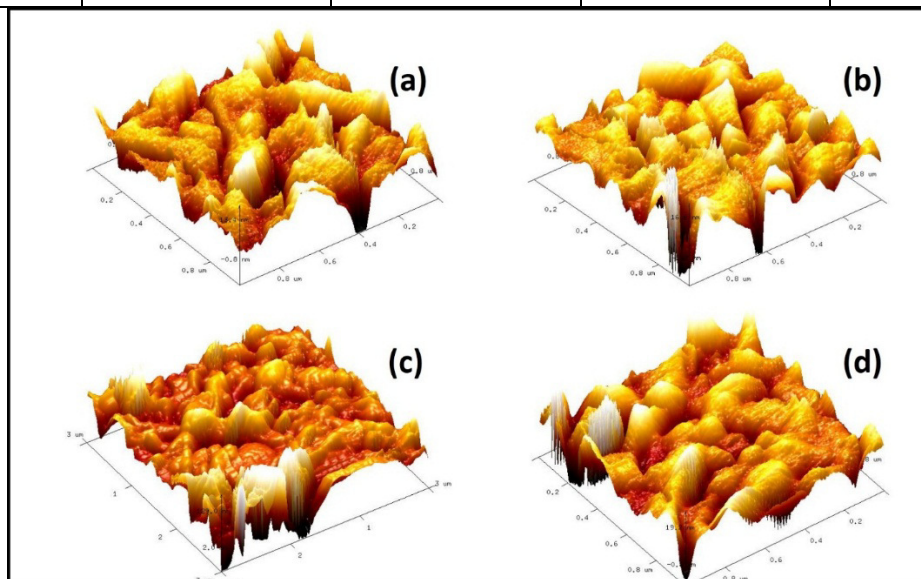


Fig. 3. 3-D AFM images of polythiophene thin films deposited at (a) 0.5, (b) 1.0, (c) 1.5 and (d) 2.0 M thiophene concentration.

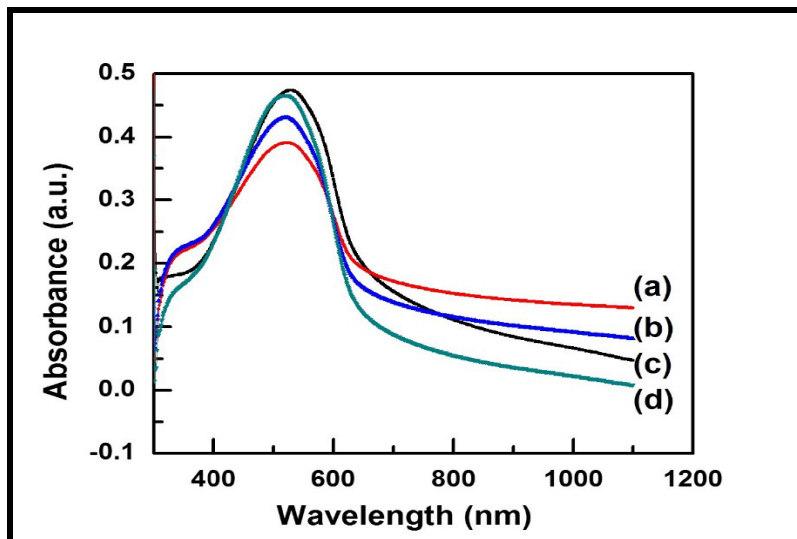


Fig. 3. UV-Visible spectra of polythiophene thin films deposited at (a) 0.5, (b) 1.0, (c) 1.5 and (d) 2.0 M thiophene concentration.

3.4 Optical study

Absorption spectra of polythiophene thin film were recorded over the spectral range of 400 to 1100 nm for different monomer concentration (Fig.4). With the increase in monomer concentration the absorbance of the film were increased. The UV-visible spectra shows a single wide peak at about 525 to 532 nm. The formation of peak is due to transition of electron from π to π^* .

3.5 Water contact angle study

The water adsorption study was carried by using wettability of the film. The hydrophobicity of the INPTh thin film was estimated by using water contact angle measurement. The contact angle is related with the roughness of the film. According to Wenzel, a surface is termed hydrophobic when contact angle is greater than 90° . The water contact angle with INPTh thin film were showed in Fig. 5. The water made contact angle with INPTh thin films are 112° , 104° , 92° and 102° showed the hydrophobic in nature of the films.

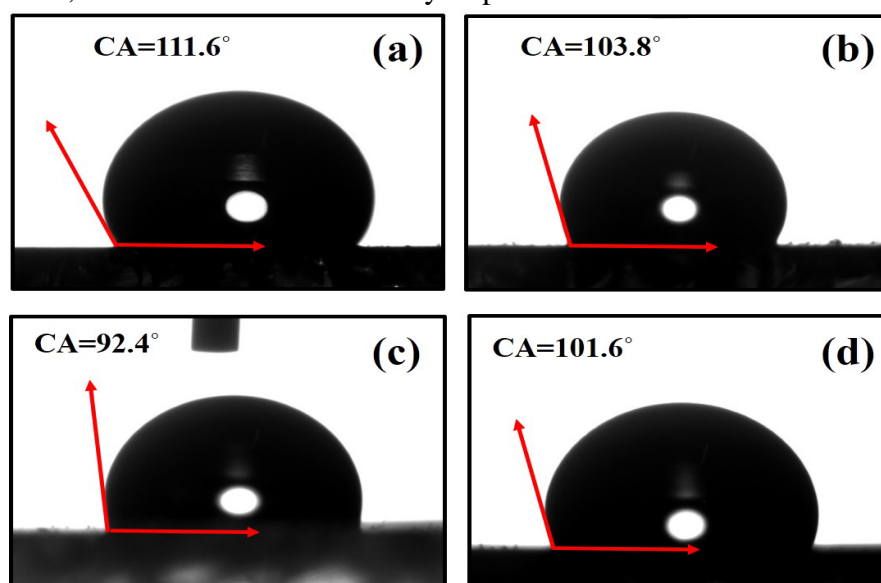


Fig. 5. Contact angle images of polythiophene thin films deposited at (a) 0.5, (b) 1.0, (c) 1.5 and (d) 2.0 M thiophene concentration.

4. Conclusion

Effect of monomer concentration on physic-chemical and optical properties were studied. The FTIR spectra shows that the chemical nature and composition of polythiophene which reveal that formation of polythiophene using chemical bath deposition technique. Structural characterization showed film were fibrous mesh like structure with high surface area. AFM study reveal that the average roughness increases with increase in monomer concentration. The water made contact angle with polythiophene thin films are showed the hydrophobic in nature of the films.

References:

- [1] B.H. Patil, A.D. Jagadale, C.D. Lokhande, Synthesis of polythiophene thin films by simple successive ionic layer adsorption and reaction (SILAR) method for supercapacitor application, *Synth. Met.* 162 (2012) 1400.
- [2] L. Torsi, A. Tafuri, N. Cioffi, M.C. Gallazzi, A. Sassella, Regioregular polythiophene field-effect transistors employed as chemical sensors, *Sens. Actuators B Chem.* 93 (2003) 257.
- [3] P. Schottland, M. Bouguettaya, C. Chevrot, Soluble polythiophene derivatives for NO₂ sensing applications, *Synth. Met.* 102 (1999) 1325.
- [4] D. B. Kamble, A.K. Sharma, J B. Yadav, V. B. Patil, R. S. Devan, A. A. Jatratar, M.A. Yewale, V.V. Ganbavle, S.D. Pawar, Facile chemical bath deposition method for interconnected nanofibrous polythiophene thin films and their use for highly efficient room temperature NO₂ sensor application, *Sensors and Actuators B* 244 (2017) 522.
- [5] N.S. Sariciftci, D. Braun, C. Zhang, V.I. Srdanov, A.J. Heeger, G. Stucky, et al., Semiconducting polymer-buckminsterfullerene heterojunctions: diodes-photodiodes, and photovoltaic cells, *Appl. Phys. Lett.* 62 (1993) 585.
- [6] M. Nasrollahzadeh, M. Jahanshahi, M. Salehi, M. Behzad, H. Nasrollahzadeh, Synthesis and characterization of nanostructured polythiophene in aqueous medium by soft-template method, *J. Appl. Chem.* 8 (2013) 31.
- [7] M. A. Loi, Q. Cai, H.R. Chandrasekhar, M. Chandrasekhar, W. Graupner, G. Bongiovanni, et al., High pressure study of the intramolecular vibrational modes in sexithiophene single crystals, *Synth. Met.* 116 (2001) 321.
- [8] T. Teslaru, I. Topala, M. Dobromir, V. Pohoata, L. Curecheriu, N. Dumitrascu, Polythiophene films obtained by polymerization under atmospheric pressure plasma conditions, *Mater. Chem. Phys.* 169 (2016) 120.
- [9] O. Inganäs, B. Liedberg, W. Chang-Ru, A new route to polythiophene and copolymers of thiophene and pyrrole, *Synth. Met.* 11 (1985) 239.
- [10] M. Xu, J. Zhang, S. Wang, X. Guo, H. Xia, Y. Wang, et al., Gas sensing properties of SnO₂ hollow spheres/polythiophene inorganic-organic hybrids, *Sens. Actuators B Chem.* 146 (2010) 8.